

AFRL-PR-WP-TP-2006-221

**Tb AND Ce DOPED Y123 FILMS
PROCESSED BY PULSED LASER
DEPOSITION**

**Joseph W. Kell, Timothy J. Haugan, Mary Frances Locke,
and Paul N. Barnes**



MAY 2004

Approved for public release; distribution is unlimited.

STINFO COPY

**This is a work of the United States Government and is not subject to copyright protection
in the United States.**

**PROPULSION DIRECTORATE
AIR FORCE MATERIEL COMMAND
AIR FORCE RESEARCH LABORATORY
WRIGHT-PATTERSON AIR FORCE BASE, OH 45433-7251**

REPORT DOCUMENTATION PAGE					Form Approved OMB No. 0704-0188	
The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.						
1. REPORT DATE (DD-MM-YY) May 2004		2. REPORT TYPE Journal Article Postprint		3. DATES COVERED (From - To) 05/10/2003 – 05/10/2004		
4. TITLE AND SUBTITLE Tb AND Ce DOPED Y123 FILMS PROCESSED BY PULSED LASER DEPOSITION				5a. CONTRACT NUMBER In-house		
				5b. GRANT NUMBER		
				5c. PROGRAM ELEMENT NUMBER 61102F/62203F		
6. AUTHOR(S) Joseph W. Kell, Timothy J. Haugan, Mary Frances Locke, and Paul N. Barnes				5d. PROJECT NUMBER 3145		
				5e. TASK NUMBER 32		
				5f. WORK UNIT NUMBER 314532Z9		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Power Generation Branch (AFRL/PRPG) Power Division Propulsion Directorate Air Force Research Laboratory, Air Force Materiel Command Wright-Patterson Air Force Base, OH 45433-7251				8. PERFORMING ORGANIZATION REPORT NUMBER AFRL-PR-WP-TP-2006-221		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Propulsion Directorate Air Force Research Laboratory Air Force Materiel Command Wright-Patterson AFB, OH 45433-7251				10. SPONSORING/MONITORING AGENCY ACRONYM(S) AFRL-PR-WP		
				11. SPONSORING/MONITORING AGENCY REPORT NUMBER(S) AFRL-PR-WP-TP-2006-221		
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.						
13. SUPPLEMENTARY NOTES Journal article postprint published in IEEE Transactions on Applied Superconductivity, Vol. 15, No. 2, June 2005. PAO case number: AFRL/WS 04-1252; Date cleared: 16 Nov 2004. This is a work of the U.S. Government and is not subject to copyright protection in the United States.						
14. ABSTRACT To evaluate possible flux pinning enhancement in YBa ₂ Cu ₃ O _{7-x} (Y123) films due to partial rare-earth ion substitutions, Ce and Tb doping are studied. Bulk ceramic targets of varying compositions (Y _{1-x} RE _x Ba ₂ Cu ₃ O _{7-x}) were made with several doping levels (x = 0.001 to 0.1, RE = Ce or Tb) by using regular solid-state reaction and sintering procedures. These targets were used to deposit Ce and Tb doped YBCO films onto SrTiO ₃ single crystal substrates by pulsed laser ablation. Doped YBCO films were characterized for T _c , magnetic field dependence of J _c (at 77 K), microstructure, and other properties. The results are compared to undoped YBCO films processed in similar manner.						
15. SUBJECT TERMS High-temperature superconductors, magnetic field measurement, superconducting materials, thin films						
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT: SAR	18. NUMBER OF PAGES 10	19a. NAME OF RESPONSIBLE PERSON (Monitor) Paul N. Barnes	
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include Area Code) N/A	

Tb and Ce Doped Y123 Films Processed by Pulsed Laser Deposition

Joseph W. Kell, Timothy J. Haugan, *Member, IEEE*, Mary Frances Locke, and Paul N. Barnes

Abstract—To evaluate possible flux pinning enhancement in $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ (Y123) films due to partial rare-earth ion substitutions, Ce and Tb doping are studied. Bulk ceramic targets of varying compositions ($\text{Y}_{1-x}\text{RE}_x\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$) were made with several doping levels ($x = 0.001$ to 0.1 , $\text{RE} = \text{Ce}$ or Tb) by using regular solid-state reaction and sintering procedures. These targets were used to deposit Ce and Tb doped YBCO films onto SrTiO_3 single crystal substrates by pulsed laser ablation. Doped YBCO films were characterized for T_c , magnetic field dependence of J_c (at 77 K), microstructure, and other properties. The results are compared to undoped YBCO films processed in similar manner.

Index Terms—High-temperature superconductors, magnetic field measurement, superconducting materials, thin films.

I. INTRODUCTION

COATED conductors using biaxially aligned $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (Y123) on buffered metallic substrates have been shown to have high critical current densities (J_c) $> 10^6$ A/cm² and good flux pinning characteristics in applied magnetic fields [1]–[3]. As such, Y123 has great promise as a second generation high temperature superconducting (HTS) wire for use in generators and motors as well as in other important electrical devices [4]–[6]. However, when magnetic fields are applied parallel to the c-axis, J_c tends to decrease one to two orders of magnitude when fields of between 1 T and 5 T are applied [7], [8]. This shows that further improvement of J_c is desired, especially when subjected to high magnetic fields in the c-axis orientation. This is especially important when a reduction of system weight and size is desired, e.g. superconducting generators and motors. It is also important to increase J_c since the upper design limit of the magnetic field for a given coil design is generally based upon the value of $J_c(H)$.

One way to improve the flux pinning characteristics of type-II superconductors is to introduce secondary superconducting phases into the material [1]–[3]. Since Y123 and other RE123 materials have similar structures, this can be accomplished by substituting other rare earth elements for yttrium in Y123 films. However, only a few of the rare earth elements have been shown to not form a pure RE123 phase. In this work, two of these elements, Tb and Ce, are used to substitute for Y in Y123 thin films. Both have been noted in the literature as not

forming the RE123 phase, at least in bulk powders [9]. Both of these elements are divalent, having both +3 and +4 valence states. These states will possibly allow the two elements to act as pinning sites by alternate chemical bonding. Assuming a fully homogenous structure, the size of the pinning particles would approximately be the size of the RE123 unit cell. The nature of pinning could potentially be nonsuperconducting inclusions/sites in addition to or in lieu of strain induced improvements due to slight changes in the unit cell. The possibility of nonsuperconducting locations is reasonable to consider due to the difficulty in forming the RE123 phase with Tb and Ce.

However, Ce and Tb do differ substantially in other properties. Terbium does not degrade the T_c of Y123; in contrast, Ce affects the T_c s of Y123 by substantially lowering them with increasing Ce content in bulk material [10]. In addition, terbium has a similar ionic radius (1.04 Å) to yttrium (1.019 Å), while Ce is significantly larger (1.143 Å). Using small quantities of dopants allows for the same deposition parameters as in high quality Y123 during PLD. This allows for previously optimized O_2 pressures and laser fluences to be used, thereby reducing the processing time and simplifying the depositions.

Since Tb and Ce have these specific differences from the other rare earths, this study focuses on substituting small quantities ($x \leq 0.1$) of Tb and Ce for Y in Y123 thin films. In so doing, appropriate defect densities of the inclusions will be produced if the inclusions are sufficiently dispersed. Previous studies have focused on substituting large quantities of Tb for Y in Y123 ($x \geq 0.1$) [10]–[12] and hence lack any noteworthy success.

II. EXPERIMENTAL

The laser ablation targets were manufactured in-house. Three primary powders were prepared with compositions of $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$, $\text{Y}_{0.90}\text{Tb}_{0.10}\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$, and $\text{Y}_{0.90}\text{Ce}_{0.10}\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$ from the precursor powders Y_2O_3 , BaCO_3 , CuO , CeO_2 , and Tb_4O_7 powder (all nominally 99.99+% pure). The powders were dried, mixed, and then calcined at 850°C and 880°C. The resultant powder was then used to make targets of compositions $\text{Y}_{0.9}\text{Tb}_{0.1}\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$, $\text{Y}_{0.99}\text{Tb}_{0.01}\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$, $\text{Y}_{0.999}\text{Tb}_{0.001}\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$, $\text{Y}_{0.90}\text{Ce}_{0.10}\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$, $\text{Y}_{0.99}\text{Ce}_{0.01}\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$, and $\text{Y}_{0.999}\text{Ce}_{0.001}\text{Ba}_2\text{Cu}_3\text{O}_{7-x}$ by diluting the initial ($\text{Y}_{0.90}, \text{Tb}_{0.10}$)123 and ($\text{Y}_{0.90}, \text{Ce}_{0.10}$)123 doped powder with Y123. The targets were then fully reacted and sintered at 940°C until they reached a density of $>80\%$ theoretical density. The estimated purity of the targets was 99.99+%.

The multiple compositions of (Y,Tb)123 and (Y,Ce)123 films were deposited by pulsed laser deposition, using parameters and

Manuscript received October 5, 2004. This work was supported in part by the Air Force Office of Scientific Research.

The authors are with the Air Force Research Laboratory, WPAFB, OH 45433-7919 USA (e-mail: joseph.kell@wpafb.af.mil; timothy.haugan@wpafb.af.mil; mary.locke@wpafb.af.mil; paul.barnes@wpafb.af.mil).

Digital Object Identifier 10.1109/TASC.2005.849415

TABLE I
SUMMARY OF MAGNETIC DATA FOR Tb AND Ce DOPED Y123

Film Composition	T _c (DC Magnetization)	J _c @ 77K and 0.01T Applied Field	J _c @ 65K and 0.01T Applied Field	J _c @ 77K and 2T Applied Field	J _c @ 65K and 2T Applied Field
Y-123	89.2 K	2.23 MA/cm ²	5.87 MA/cm ²	0.140 MA/cm ²	0.78 MA/cm ²
(Y _{0.999} Tb _{0.001})-123	88.0 K	3.13 MA/cm ²	9.01 MA/cm ²	0.107 MA/cm ²	1.24 MA/cm ²
(Y _{0.99} Tb _{0.01})-123	89.0 K	2.68 MA/cm ²	8.29 MA/cm ²	0.162 MA/cm ²	1.53 MA/cm ²
(Y _{0.90} Tb _{0.10})-123	89.5 K	3.43 MA/cm ²	9.54 MA/cm ²	0.100 MA/cm ²	0.70 MA/cm ²
(Y _{0.999} Ce _{0.001})-123	88.9 K	1.65 MA/cm ²	5.66 MA/cm ²	0.099 MA/cm ²	1.11 MA/cm ²
(Y _{0.99} Ce _{0.01})-123	88.5 K	2.10 MA/cm ²	5.44 MA/cm ²	0.056 MA/cm ²	0.59 MA/cm ²
(Y _{0.90} Ce _{0.10})-123	84.8 K	0.52 MA/cm ²	2.86 MA/cm ²	0.001 MA/cm ²	0.21 MA/cm ²

conditions optimized previously for Y123 [13]–[15]. The depositions were performed on strontium titanate (STO) and lanthanum aluminate (LAO) substrates with the overall time for film growth being about 20 minutes. The LAO (100) and STO (100) single crystal substrates were ultrasonically cleaned for 2 minutes, using first acetone followed by isopropyl alcohol. Crystalline substrates were provided by the manufacturer epitaxially polished on both sides of the LAO and on one side for STO, and were attached to the heater using a thin layer of colloidal Ag paint. LAO and STO substrates sizes were $\sim 3.2 \text{ mm} \times 3.2 \text{ mm}$ for magnetic J_c measurements.

Depositions were performed using a Lambda Physik, LPX 305 KrF excimer laser ($\lambda = 248 \text{ nm}$). The laser pulse rate was 4 Hz and the laser fluence was $\sim 3.2 \text{ J/cm}^2$. The target-to-substrate distance was kept at 6 cm for all of the depositions. The background pressure in the chamber was reduced to $< 6 \times 10^{-6}$ Torr prior to depositions. The oxygen pressure during the deposition was 300 mTorr for all targets, as measured with capacitance manometer and convectron gauges within $< 10\%$ variation. Oxygen gas (99.999% purity) flowed into the chamber during growth and the oxygen pressure in the chamber was kept constant using a downstream throttle-valve control on the pumping line. Rastering of the targets was performed, along with scanning of the laser beam across the surface of the targets to improve thickness uniformity of the films.

Samples were heated from room temperature to the deposition temperature of 780°C at $\sim 1270^\circ\text{C/h}$. After deposition, the vacuum pumps and O₂ pressure control were shut off and the films were cooled from 780°C to 500°C while increasing the O₂ pressure to 1 Atm. The temperature was then held at 500°C for 30 minutes. The films were then cooled to room temperature. The (Y,Tb)123 layer thickness was initially estimated by comparing previous deposition runs in the chamber using the same deposition parameters.

The superconducting transition temperature (T_c) and magnetic J_c measurements were made with a Quantum Design Model 6000 Physical Property Measurement System (PPMS) with a vibrating sample magnetometer (VSM) attachment. The T_cs of the films were determined using a DC magnetization technique. The samples were mounted onto the end of a G-10 fiberglass rod and the magnetic moment of the material was measured as the samples were warmed from 60 K to 100 K at $\sim 0.5 \text{ K/min}$. The magnitude of the applied field was 0.0025 T. The T_c measurements were precise to within 0.1 K.

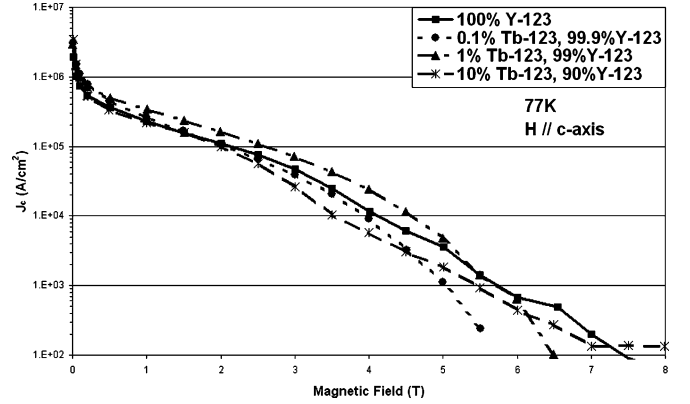


Fig. 1. Magnetic field dependence of J_c for Tb doped Y123 films at 77 K.

The magnetic J_c measurements were determined by subjecting the films to applied fields that varied from 0 to 9 T, with a ramp rate of 0.01 T/s. The J_c of the square samples was estimated using a simplified Bean model with $J_c = 30 \Delta M / da^3$ where ΔM is in emu, film thickness d and lateral dimension a are in cm and J is in A/cm² [16]. Samples were subsequently acid-etched at the corners for thickness measurements. A KLA Tencor P-15 Profilometer was used to measure the thickness of the (Y,Tb)123 and (Y,Ce)123 films. Care was used to measure in twin-free areas of the LAO substrates, which were observed visually at high magnification. The film thickness and dimensions of each sample were measured multiple times to reduce errors in determination of the superconducting volume and a to $< 5\%$.

III. RESULTS AND DISCUSSION

The T_cs of the films as measured by DC magnetization are shown in Table I. As can be seen in the table, the T_cs of Tb doped films (between 88.0 K and 89.5 K) are comparable to the T_c of reference Y123 films (89.2 K). However, the Ce doped films showed a marked decrease in T_c as the concentration of Ce increased, reaching a low value of 84.8 K. This is likely due to the Ce preferring to exist in a tetravalent state.

The magnetic J_cs of the Tb and Ce doped films are also given in Table I. The graphs showing the magnetic field dependence of J_c for the films are in Figs. 1–4. Figs. 1 and 2 show magnetic field dependence of J_c at 77 K for Tb and Ce doped samples respectively. Figs. 3 and 4 show magnetic field dependence of J_c at 65 K for Tb and Ce doped Y123 respectively. At 0.01 T, the J_cs of the Tb doped samples were all above 1 MA/cm² while the

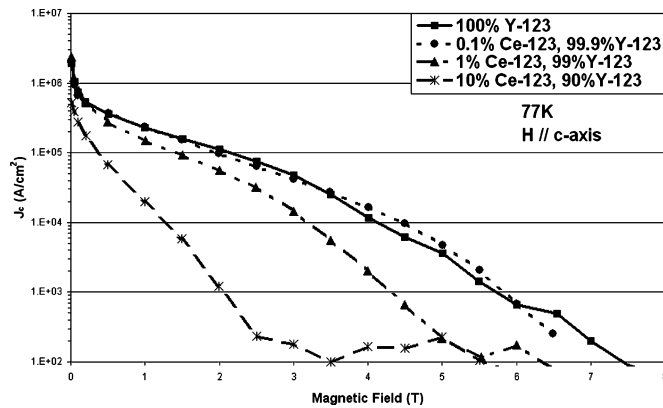


Fig. 2. Magnetic field dependence of J_c for Ce doped Y123 films at 77 K.

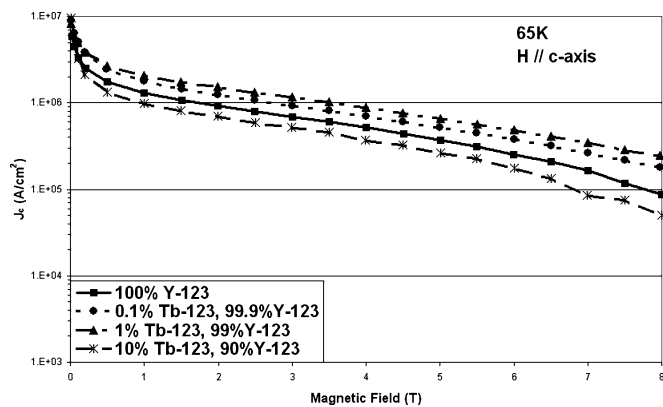


Fig. 3. Magnetic field dependence of J_c for Tb doped Y123 films at 65 K.

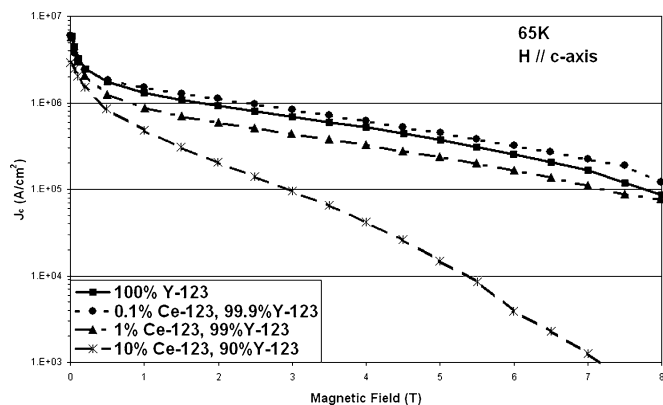


Fig. 4. Magnetic field dependence of J_c for Ce doped Y123 films at 65 K.

Ce samples J_c s decreased with increasing concentration of Ce from 1.65 MA/cm^2 for $(\text{Y}_{0.999}\text{Ce}_{0.001})_{123}$ to $\sim 0.5 \text{ MA/cm}^2$ for $(\text{Y}_{0.90}\text{Ce}_{0.10})_{123}$.

The most important feature of these results is that, at higher concentrations of 10% or greater (typically used for rare earth substitutions in Y123), these elements are detrimental to the in-field current density of YBCO, this is especially true in the case of Ce addition. This is constant with prior work indicating the degrading nature of these elements as inclusions into the Y123 structure [10]. However, when concentrations are reduced to

smaller proportions, enhancement of J_c is possible. At 65 K, this is particularly apparent with 0.1% and 1% Tb and 0.1% Ce additions. The difference between the 1% Tb concentration and the 1% Ce concentration can be ascribed to the degrading effects of Ce on T_c , per previous work, whereas Tb does not produce such reductions in T_c . Perhaps the greater difficulty of this process for introducing pinning is obtaining a well dispersed mixture of $<0.1\%$ Tb or Ce. If possible, it is projected that better pinning properties can be realized, especially with Ce.

IV. CONCLUSIONS

Tb and Ce doped Y123 films were processed by PLD. Results suggest that doping Y123 with Tb produces films of good quality with similar properties to that of Y123. Decreasing the quantity of Tb to 1% or less appears to produce enhanced pinning characteristics of the resulting films especially at higher fields. However, the addition of Ce to Y123 films produces films of increasingly poorer quality as the concentration of Ce is increased in the films. However, it does appear that very minute additions of Ce ($\sim 0.1\%$ Ce123 in Y123) may actually produce some favorable pinning characteristics to the films at high fields at 65 K.

ACKNOWLEDGMENT

J. W. Kell thanks L. Brunke, J. Evans, and J. Murphy from the Propulsion Directorate, Air Force Research Laboratory, WPAFB, OH for assistance in setting up equipment, characterizing samples, and analyzing data. J. W. Kell would also like to thank C. Varanasi and all others who reviewed this paper for their helpful comments, which greatly improved the quality of this paper.

REFERENCES

- [1] Y. Iijima, K. Onabe, N. Tugaki, N. Tanabe, N. Sadakara, O. Kohno, and Y. Ikeno, "In-plane aligned $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ thin films deposited on polycrystalline metallic substrates," *Appl. Phys. Lett.*, vol. 60, no. 6, pp. 769–771, 1992.
- [2] X. D. Wu, S. R. Foltyn, P. N. Arendt, W. R. Blumenthal, I. H. Campbell, J. D. Cotton, J. Y. Coulter, W. L. Hults, M. P. Maley, H. F. Safar, and J. L. Smith, "Properties of $\text{YBa}_2\text{Cu}_3\text{O}_7$ —thick films on flexible buffered metallic substrates," *Appl. Phys. Lett.*, vol. 67, no. 16, pp. 2397–2399, 1995.
- [3] A. Goyal, D. P. Norton, J. D. Budai, M. Paranthaman, E. D. Specht, D. M. Kroeger, D. K. Christen, Q. He, B. Saffian, F. A. List, D. F. Lee, P. M. Martin, P. M. Klabunde, E. Hartfield, and V. K. Sikka, "High critical current density superconducting tapes by epitaxial deposition of $\text{YBa}_2\text{Cu}_3\text{O}_x$ thick films on biaxially textured metals," *Appl. Phys. Lett.*, vol. 69, no. 12, pp. 1795–1797, 1996.
- [4] P. N. Barnes, G. L. Rhoads, J. C. Tolliver, M. D. Sumption, and K. W. Schmaeman, "Compact, lightweight superconducting power generators," *IEEE Trans. Mag.*, to be published.
- [5] D. Larbalestier, A. Gurevich, D. M. Feldmann, and A. Polyanskii, "High- T_c superconducting materials for electric power applications," *Nature*, vol. 414, pp. 368–377, 2001.
- [6] D. C. Larbalestier and M. P. Maley, "Conductors from superconductors; conventional low-temperature and new high-temperature superconducting conductors," *MRS Bulletin*, vol. 18, no. 8, pp. 50–56, 1993.
- [7] S. R. Foltyn, E. J. Peterson, J. Y. Coulter, P. N. Arendt, Q. X. Jia, P. C. Dowden, M. P. Maley, X. D. Wu, and D. E. Peterson, "Influence of deposition rate on the properties of thick $\text{YBa}_2\text{Cu}_3\text{O}_{7-d}$ films produced by pulsed laser deposition," *J. Mater. Res.*, vol. 12, no. 11, pp. 2941–2946, 1997.

- [8] T. Aytug, M. Paranthaman, S. Sathyamurthy, B. W. Kang, D. B. Beach, E. D. Specht, D. F. Lee, R. Feenstra, A. Goyal, D. M. Kroeger, K. J. Leonard, P. M. Martin, and D. K. Christen, "ORNL superconducting technology program for electric power systems, annual report for FY 2001," Oak Ridge Nat. Lab., <http://www.ornl.gov/HTSC/htsc.html>.
- [9] S. Tsurumi, M. Hikita, T. Iwata, K. Semba, and S. Kurihara, "High T_c superconductivities of $A_2Ba_4Cu_6O_{14+y}$," *Jpn. J. Appl. Phys.*, vol. 26, no. 5, pp. L856–L857, May 1987.
- [10] C. R. Fincher Jr. and G. B. Blanchet, "Ce and Tb substitution for Y in $YBa_2Cu_3O_7$ thin films," *Phys. Rev. Lett.*, vol. 67, no. 20, pp. 2902–2905, Nov. 1991.
- [11] U. Staub, M. R. Antonio, and L. Soderholm, "Tb oxidation state and hybridization in $Y_{0.9}Tb_{0.1}Ba_2Cu_3O_{7-\delta}$ ($\delta = 0.02, 0.84$): a magnetic-susceptibility and x-ray-absorption study," *Phys. Rev. B*, vol. 50, no. 10, pp. 7085–7091, Sep. 1994.
- [12] J. W. Kell, T. J. Haugan, P. N. Barnes, C. V. Varanasi, L. B. Brunke, M. F. Locke, and T. A. Campbell *et al.*, "Processing and characterization of $(Y_{1-x}Tb_x)Ba_2Cu_3O_{7-z}$ superconducting thin films prepared by pulsed laser deposition," in *Ceramic Transactions*, P. Paranthaman and P. Barnes, Eds. Westerville, OH: American Ceramic Society, 2004.
- [13] T. J. Haugan, P. N. Barnes, R. Wheeler, F. Meisenkothen, and M. Sumption, "Addition of nanoparticle dispersion to enhance flux pinning of the $YBa_2Cu_3O_{7-x}$ superconductor," *Nature*, vol. 430, no. 19, pp. 867–870, 2004.
- [14] T. J. Haugan *et al.*, "Island growth of Y_2BaCuO_5 nanoparticles in $(211 \sim 1.5 \text{ nm} / 123 \sim 10 \text{ nm}) \times N$ composite multilayer structures to enhance flux pinning of $YBa_2Cu_3O_{7-x}$ films," *J. Mater. Res.*, vol. 18, pp. 2618–2623, 2003.
- [15] T. J. Haugan, P. N. Barnes, L. B. Brunke, I. Maartense, and J. Murphy, "Effect of O_2 partial pressure on $YBa_2Cu_3O_{7-x}$ thin film growth by pulsed laser deposition," *Physica C*, vol. 297, pp. 47–57, 2003.
- [16] J. D. Doss, "The phenomena of superconductivity: fundamental considerations," in *Engineer's Guide to High-Temperature Superconductivity*. New York: John Wiley & Sons, 1989, pp. 41–96.